



M2 HIGH SPEED STEEL

COMPOSITION %	C*	Cr	Mo	W	V
	0.90	4.20	5.0	6.40	1.80
STANDARDS	AISA M2, W.Ne.3343, SI 6-5-2, DM05, SS 2722, ISO S4, JIS SKH51, AFNOR Z85WDCV 6.5.4.2				
CONDITION AS	Soft-annealed		Max 260 HB		
AS SUPPLIED	Cold Drawn		Max 300 HB		
	Cold Rolled		Max 310 HV		

* Strips C 0.85 %

M2 is a conventionally manufactured high-speed steel. The various stages of the manufacturing process are chosen and controlled so that an end product is obtained with a good structure in terms of carbide size and distribution. This is a distinct advantage for the finished tool.

M2 is characterised by

- all-round applicability
- good machine-ability
- good performance

APPLICATIONS

M2 is a high-speed steel suitable for cutting tools such as, twist drills, broaches, taps, milling cutters, reamers, saws, knives etc. In terms of performance, M2 is an all-round steel to be used in cutting conditions where demands for hot hardness are moderate. The term hot hardness is understood as the ability of the steel to retain its hardness even at elevated temperatures. M2 is also suitable for cold work applications, e.g. in tools for punching, forming and pressing, etc. The steel possesses an admirable combination of wear resistance and toughness and in these respects is superior to the high alloyed cold work steels.

PROPERTIES

M2 is medium-alloyed and has a good machinability. The composition of M2 makes for a good combination of toughness and hardness. By virtue of these well-balanced properties M2 has come into very wide use for all cutting tools.

PHYSICAL PROPERTIES


		TEMPERATURE °C / °F		
		20 / 70	400 / 750	600 / 1110
DENSITY	Kg/m ³	8160	8060	8000
	lbs/in ³	.295	.291	.289
MODULUS OF ELASTICITY	kN/mm ²	225	200	180
	psi	$33 \cdot 10^6$	$29 \cdot 10^6$	$26 \cdot 10^6$
COEFFICIENT OF THERMAL EXPANSION FROM 20°C / 70°F	per °C	-	$12.1 \cdot 10^{-6}$	$12.6 \cdot 10^{-6}$
	per °F	-	$6.7 \cdot 10^{-6}$	$7.0 \cdot 10^{-6}$
THERMAL CONDUCTIVITY	W/m °C	24	28	27
	Btu/sq. ft. h °F/in.	166	194	187
SPECIFIC HEAT	J/kg °C	420	510	600
	Btu/lb °F	0.10	0.12	0.14

METHODS OF MAKING TOOLS

M2 can be worked in the same way as other high-speed steels by plastic forming, machining, grinding, electrical discharge machining, welding and polishing. M2 is amenable to cold forming. In grinding, local heating of the surface, which might alter the microstructure, must be avoided. Grinding wheel makers can supply advice on the choice of grinding wheels. Machining is carried out using carbide or high speed steel tools.

BEND STRENGTH

The bend strength is a measure of the toughness of the material. It will be seen from the diagram that toughness and hardness can be controlled by varying the hardening temperature.

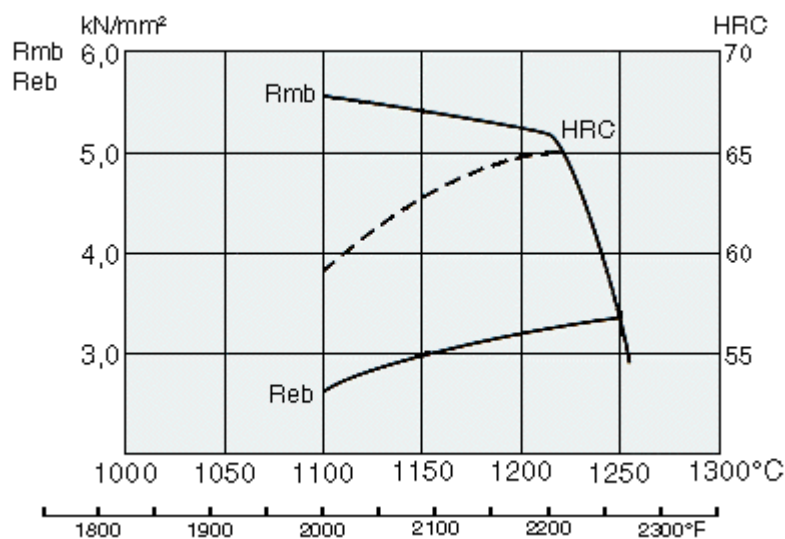

Bend strength of a bar with diameter 5 mm after hardening and tempering to 560°C / 1040°F, 2x1 h.


Rmb = Ultimate bend strength kN/mm², ± 10%

Reb = Bend yield strength kN/mm², ± 5%

HRC = Hardness ± 1 HRC

HEAT TREATMENT

- Soft-annealing 850°C – 900°C / 1560°F – 1650°F, slow cooling 10°C / 18°F/h to 700°C / 1290°F, hardness max 260 Brinell.
- Stress relieving 600°C – 700°C / 1120°F – 1290°F, approx. 2 hours at temperature, slow cooling to 500°C / 930°F.
- Hardening with preheating in two steps 450°C – 500°C / 840°F – 930°F, 850°C – 900°C / 1560°F – 1650°F and austenitizing at 1050°C – 1220°C / 1920°F – 2230°F. Quenching to about 550°C / 1022°F then air cooling down to room temperature.
- 2 temperings at 560°C / 1040°F are recommended (maintaining at least one hour each at temperature).

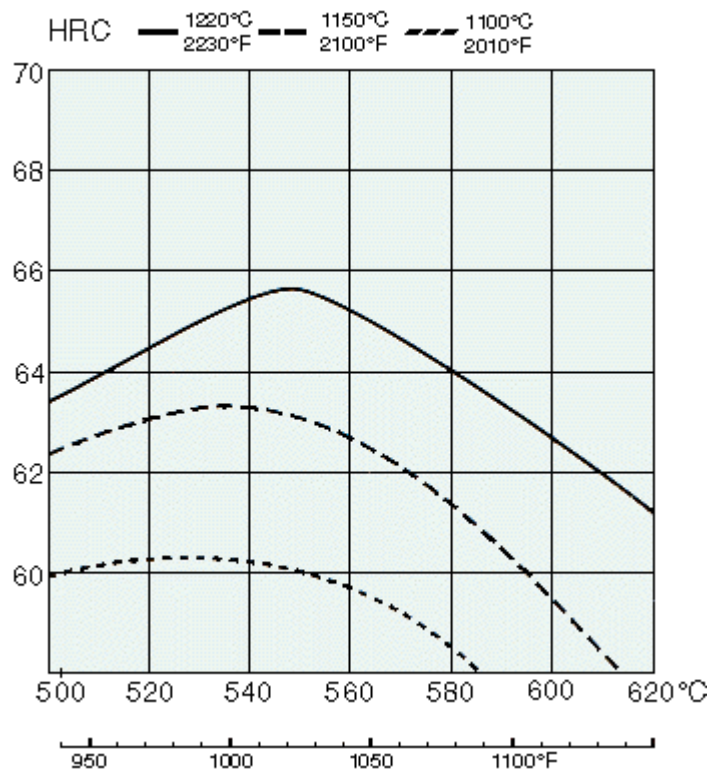

Hardness after hardening, step quenching and tempering 2x1 h of a sample 25 mm Ø.

SURFACE TREATMENT

M2 can be nitrided (a small diffusion zone of 2–20 µm is recommended) or steam - tempered if so desired. M2 is good as substrate material for PVD and CVD coating.

GUIDELINES FOR HARDENING

TOOL	M2	
	Hardening	Tempering 2x1H
Single- edge cutting tools, tool bits, form tools, etc.	1220°C 2230°F	560°C 1040°F
Rotating multi-edge cutting tools, twist drills, saws, milling cutters broaches, taps, etc.	1180°C – 1220°C 2155°F – 2230°F	560°C – 590°C 1040°F – 1095°F
Tools for cold work applications, punching, blanking, forming, cold extrusion, etc.	1050°C – 1150°C 1920°F – 2100°F	560°C – 590°C 1040°F – 1095°F

MANUFACTURING PROGRAMME

FROM	Dimensional range Th x W x L	
	mm	inches
Coils Ø	1 – 22	0.039 – 0.866
Round bars Ø	1 – 150	0.039 – 5.906
Forged bars Ø	max dia 400	max dia 15.748
Flat bars	3 – 7, 5x50 – 380	0.118 – 0.295x1.969 14.961
Square bars	4.5 – 130	0.177 – 5.118
Profiles Ø		
Strips	0.3 – 4x5 – 100	0.012 – 0.157 x0.197 – 3.937
Sheets	0.8 – 10x600x860x 800 – 2500	0.031 – 0.394x23.622 – 33.858x31.496 – 98.425
Discs	0.8 – 10 max dia 800	0.031 – 0.394 max dia 31.496
Bimetal edge	0.6 – 3x1 – 10	0.024 – 0.118x0.039 – 0.394

The surface condition is drawn, shot blasted, ground, rolled, cold rolled, hot rolled, peeled, rough-machined depending on dimensions and requirements.